



Integrated Heterogeneous Electro-Fenton Process and Constructed Wetland for the Treatment of Stabilized Landfill Leachate

X. Daniel Joseph, U. Bhuvaneshwari and K. Soundaranayaki*

Centre for Environmental Studies, Anna University, Guindy Campus, Chennai, TN, India

Received: 04.05.2024 Accepted: 22.06.2024 Published: 30.06.2024

*soundariya31@gmail.com

ABSTRACT

Treatment of stabilized landfill leachate is a great challenge due to its poor biodegradability. Present study made an attempt to treat this wastewater by combining electro-Fenton (E-Fenton) and constructed wetland (CW). E-Fenton treatment was applied prior to Constructed wetland process to enhance the biodegradability of leachate, which will be beneficial for the subsequent biological process. This study also investigates the efficiency of Magnetite (Fe_3O_4) nanoparticles as a heterogeneous catalyst in E-Fenton process. The objectives of this study are to synthesize chitosan to obtain magnetite nanoparticles via iron ions assembly and to characterize the synthesized nanoparticles using SEM, XRD and FTIR analysis to assess its nature. The effects of initial pH, catalyst dosage, applied voltage and electrode spacing on Chemical Oxygen Demand (COD) removal efficiency were analysed to determine the optimum conditions. Heterogeneous E-Fenton process gave 84.29% COD removal at catalyst dosage of 50 mg/L, pH 2, electrode spacing 3 cm, voltage 5 V and effective electrode area 25 cm². The proficiency of utilizing eggshells as a media in constructed wetlands was evaluated for the treatment of wastewater previously subjected to electro-Fenton treatment. And it was found that combined E-Fenton and biological treatment (CW) resulted in overall COD removal of 95.79%, bringing down the final COD to 292 mg/L. Thus, the combination of the E-Fenton process followed by a biological process is efficient for complete mineralization with lower operational cost.

Keywords: Stabilized landfill leachate; Electro Fenton; Constructed wetland; Magnetite nanoparticles.

1. INTRODUCTION

Urbanization is contributing to a notable increase in the generation of both solid and liquid waste and this surge in waste production poses more significant challenges for disposal processes, particularly in developing countries like India. But municipal governments face constraints due to limited finances and inadequate services (Sohail and Afzal, 2011). Landfill is a prevalent method for waste removal and disposal, represents as end point in managing municipal solid waste. This widespread practice has emerged as a significant global environmental concern, contributing to contamination and pollution (Yaashikaa *et al.* 2022). Leachate is a contaminated liquid emerging from the landfill sites and is generated through two processes (i.e.) when rainwater interacts with the waste, it permeates through, dissolving soluble substances in the process. Additionally, certain degradation reactions within the waste generate acidic liquids, which further increases the harmful nature of the resulting leachate. Leachate classification depends on the landfill's age, with categories including young ($\text{BOD}_5/\text{COD} > 0.6$), intermediate ($\text{BOD}_5/\text{COD}=0.3-0.6$), and stabilized/mature ($\text{BOD}_5/\text{COD} < 0.3$). Only in case of high BOD_5/COD ratio and elevated concentration of low

molecular weight organics in young leachate makes it well-suited for biological treatment techniques (Baiju *et al.* 2018).

Even though there are various physical and biological methods involved in the treatment of landfill leachate each has its own limitations. When treating aged landfill leachate with low biodegradability, biological processes may not achieve good results due to the stubborn nature of organic carbon, and the simultaneous high concentration of ammonia nitrogen and heavy metals in the leachate, since it has a strong retarding impact on microorganisms (Zijing *et al.* 2022). Physicochemical techniques emerge as a more suitable option for treating mature landfill leachate, characterized by a low BOD_5/COD ratio and elevated concentrations of high molecular weight refractory organics (Deng, 2007). Among the advanced physico-chemical processes such as electrocoagulation and electro-oxidation, the necessity in constant replacement of the "sacrificial anode" in electrocoagulation and formation of a sludge containing significant amounts of metal ions and persistent pollutants, posing challenges in its treatment. Additionally, electro-oxidation process has a drawback of leading to the formation of toxic chlorinated

byproducts, especially when treating landfill leachate with a high chloride ion content.

AOPs are a group of efficient technologies which helps in the removal of variety of persistent pollutants in matured leachate by the hydroxyl and sulphate radicals which has high oxidation potential. Among other different Advanced Oxidation Process (AOP), Fenton and Fenton like processes has gained much attention in recent years in refractory organics. (Bandala *et al.* 2021). In Fenton's process, Fenton's reagent is defined as the catalytic generation of hydroxyl radicals ($\bullet\text{OH}$) resulting from the chain reaction between ferrous ion and hydrogen peroxide (Zhang *et al.* 2005). In the Electro-Fenton process, which is a combination of electrochemistry and fenton's reagent, hydrogen peroxide (H_2O_2) is electrochemically generated to produce hydroxyl radicals $\bullet\text{OH}$ which are highly reactive and capable of oxidizing a wide range of organic compounds. By using carbon-based electrodes, it enhances the overall reaction rates in the Electro-Fenton process, leading to more efficient production of hydrogen peroxide. This can be attributed to the unique surface properties and conductivity of carbon materials (Klidi *et al.* 2019). In the traditional Fenton method, which employs a homogeneous catalyst, faces obstacles like a slower rate of ferrous ion regeneration and increases sludge production. In order to resolve these issues heterogeneous Electrochemical Advanced Oxidation Processes (EAOP's) has been studied lately (Baiju *et al.* 2018).

Several biological treatment methods, such as anaerobic sludge blankets (UASB), activated sludge and sequencing batch reactors (SBR), are employed for leachate treatment. However, these processes are considered costly due to high expenses associated with construction, maintenance, and operation. In contrast, constructed wetlands offer an eco-friendly and effective alternative as a secondary treatment (Bakhshoodeh *et al.* 2020). Constructed wetlands (CW) are man-made artificial treatment systems that imitate the functions of natural wetlands in a controlled condition (Wdowczyk *et al.* 2022). Constructed wetlands (CWs), recognized as effective secondary treatment systems, purify wastewater through various processes. These include physical processes like sedimentation and filtration, chemical processes such as precipitation and adsorption, and biological actions like microbial degradation, uptake from the water, and interactions in the root zone (Bakhshoodeh *et al.* 2020). Therefore, recognizing the drawbacks of electro-Fenton and constructed wetlands (CW), this study proposes an integration of these methods to collectively overcome their individual disadvantages. In the combined process, electro-fenton process as an initial step would convert the refractory organic pollutants into more biodegradable intermediates, which could be easily removed in a subsequent constructed wetland system.

2. MATERIALS AND METHOD

2.1 Study Area and Sample Collection

Leachate used in the present study was collected from Perungudi Dumping Yard which is located at 10 kms from the centre of Chennai, Tamil Nadu. The location is 1.2 km from Perungudi village and dumping yard lies between 2 km to 3 km west of Buckingham Canal and 3.5 km to 4.5 km west of Bay of Bengal Coastline. Nearly 20 L samples was collected in plastic cans and were stored at 4 °C to prevent biodegradation. Leachate characterization will be done as per standard methods.

2.2 Chemicals

Sodium molybdate (Na_2MoO_4), Orthophosphoric acid (H_3PO_4) and Ferric nitrate monohydrate ($\text{Fe}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$) were used in the catalyst preparation. Other chemicals used in the E-Fenton study include H_2SO_4 and NaOH for pH adjustment. All the chemicals used in the study were obtained from Merck and were of analytical grade.

2.3 Preparation of Catalyst

Chitosan, a polysaccharide comprising amino and acetamido groups in its monomeric units, boasts numerous primary amines ($-\text{NH}_2$) and hydroxyl ($-\text{OH}$) groups, providing active sites for effective adsorption (Bhatt *et al.* 2023). The resulting hydrogel, based on chitosan, demonstrates notable mechanical strength and chemical stability. Integrating hydrogels with chitosan elevates the overall adsorption capacity and efficiency in water treatment. The enhancement of mechanical strength in chitosan-based hydrogels can be achieved by introducing nanoparticles or crosslinking with synthetic polymers or biopolymers (Chelu *et al.* 2023). Moreover, the magnetite nanoparticles, owing to their distinctive physiochemical properties, cost-effectiveness, and facile recovery in the presence of external magnetic fields, are widely employed in water treatment applications (Aragaw *et al.* 2021).

The formulation of the catalyst has been documented earlier in (Wang *et al.* 2008) publication. The catalyst formulation involves the initial preparation of a 3% chitosan solution. This is achieved by dissolving 3 g of chitosan powder in 100 ml of a 2% (v/v) acetic acid solution. To ensure a homogeneous composition, vigorous stirring is employed, incorporating 0.3 ml of a 50% GLA (Glutaraldehyde) solution into the 100 ml chitosan solution. The solution is then left undisturbed until the chitosan hydrogel fully forms, facilitated by the cross-linking effect of GLA. This is followed by the Synthesis of Fe_3O_4 nanoparticles induced by chitosan via iron ions assembly.

The chitosan hydrogel undergoes a 30-minute soaking in FeCl_3 solution, followed by rinsing with deionized water. Subsequently, the hydrogel, now containing iron ions, is immersed in FeCl_2 solution for another 30 minutes, followed by a rinse with deionized water. This cycle is repeated three times for thorough incorporation of iron ions into the chitosan hydrogel. The resulting chitosan hydrogel with iron ions is soaked in a 5 mol/L NaOH solution for 12 hours, resulting in the formation of black Fe_3O_4 nanoparticles. To eliminate excess NaOH, the Fe_3O_4 nanoparticles in the chitosan hydrogel are washed with deionized water until the pH approaches 7, and then dried in an oven at 60 °C (Wang *et al.* 2008).



Fig. 1: Preparation of catalyst

Finally, the point of zero charge (PZC) test is conducted to identify the pH at which a particular material, such as a solid surface or colloidal particles, becomes electrically neutral. At the PZC, the surface charge is effectively neutralized, and the material exhibits minimal interaction with ions in solution (Kosmulski, 2021). It was determined by solid addition method as mentioned in (Wang *et al.* 2008) where initial pH (pH_0) values ranging from 2 to 10 will be adjusted in 100 mL conical flasks containing 45 mL of 0.1 M KNO_3 solution. After adding 1 g of magnetite to each flask, the difference between the initial and final pH values ($\Delta\text{pH} = \text{pH}_0 - \text{pH}_f$) will be plotted against the initial pH (pH_0), and the point of intersection on the resulting curve will indicate the PZC.

2.4 Experimental set up of Electro Fenton

In electro-Fenton process, the experiment will be carried out in a batch reactor consisting of 1000 mL borosilicate glass beaker with 750 mL as working volume. Graphite electrode was used as anode and cathode respectively. Dimensions of the graphite electrode were 9 cm x 8.5 cm x 0.4 cm for anode and 9 cm x 8.5 cm x 0.5 cm as cathode. For E-Fenton process, the effective area of the electrodes will be kept as 25 cm². The electrodes were connected to a DC power supply and aeration was given near cathode using a simple fish aerator for the in-situ. Samples were withdrawn at 10

minutes regular time intervals and centrifuged from which the supernatant will be collected for COD estimation. All the electrodes were thoroughly cleaned after every run with water and regularly they were soaked in 1N HCl. The electrodes were stored in distilled water when not in use.

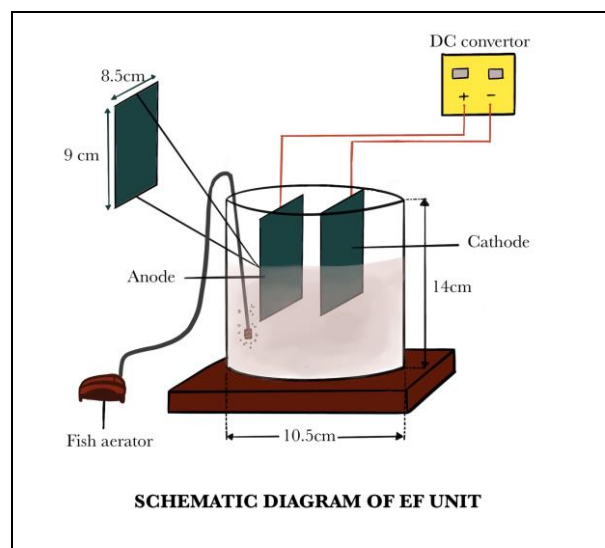


Fig. 2: Schematic representation of E-Fenton process

2.5 Experimental Setup of Constructed Wetland

Two Constructed Wetlands, CW-1 and CW-2 were fabricated using Plastic water can of dimensions (30 cm diameter, 40 cm height and 3 mm thickness). CW-1 with 2 layers consisting of top layer of 10 cm with sand (2.36 mm passing), and bottom layer of 10 cm with Gravel (5 to 10 mm) and CW-2 with 3 layers consisting of top layer of 10 cm with sand (2.36 mm passing), intermediate layer of 5 cm with Eggshell ($\leq 1\text{mm}$) and bottom layer of 5 cm with Gravel (5 to 10 mm). *Canna Indica* was collected from the Anna University STP, Chennai. The bottom ends of both systems were fitted with PVC taps (sampling port) and made water tight by sealing with epoxy; while the upper ends were left free to atmosphere. The schematic diagrams of both CW-1 and CW-2 are shown in the Fig. 3. The systems were kept in laboratory and provision for open to sky to give plant natural conditions for its growth. The experiment analysis was started after one month when two setups with vegetation grown to a good extent.

It is always preferable to choose locally available, cheap and waste material as a wetland media. The porosity and size of the media were analysed as per IS: 1498 – 1970. In CW-1 the topmost layer of the wetland was packed with sand. The mixed coarse and fine can be utilized. The collected sand was washed, dried and sieved using a sieve size 2.36 mm and the sand passing through the 2.36 mm sieve was taken for this study. The porosity of the sand is 35%. The bottom layer of the wetland was packed with gravel. In CW-2, which

consists of 3 layers consisting of top layer of 10 cm with sand (2.36 mm passing), intermediate layer of 5 cm with Eggshell (≤ 1 mm) and bottom layer of 5 cm with Gravel (5 to 10 mm). The eggshells were washed, dried in the oven and crushed to size ≤ 1 mm. Both sand and gravel were collected from an ongoing construction site at Anna University campus, Chennai. The collected gravel was washed, dried and sieved using a sieve size less than 2 mm, passed on 4 mm and retained on 3 mm. Gravel was used as supporting media for the above filter bed. It also acts as an attaching media for the microbes and for easy drainage of the leachate. The porosity of the gravel is 30% and 27% respectively.

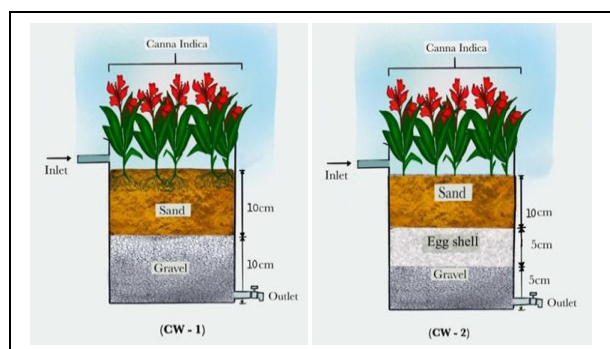


Fig. 3: Schematic representation of CW-1 and CW-2

3. RESULTS AND DISCUSSION

3.1 Characterization of Leachate

The leachate sample is collected from Perungudi dumpsite, Chennai and allowed for testing the influent characteristics of different physical and chemical parameters. The influent colour is noticed to be grey to black in colour. Leachate characterization was done as per standard methods and the obtained results are given in Table 1. The collected leachate had a pH of 8.41 and BOD/COD value of 0.169, and can thus be categorized as stabilized landfill leachate. Chemical Oxygen Demand (COD) of stabilized landfill leachate will normally be less than 4000 mg/L, but the collected leachate had COD higher than 4000 mg/L. Similar results have been reported by (Baiju *et al.* 2018).

Table 1. Initial parameters of leachate

Experiment	Unit	Influent	Average
pH	-	8.29	8.54
Electrical Conductivity	$\mu\text{S}/\text{cm}$	30400	29360
BOD	mg/L	1110	1250
COD	mg/L	6880	7010
BOD/COD	-	0.161	0.178
TDS	mg/L	44000	44880
TSS	mg/L	650	660
TS	mg/L	44650	45540
Cl	mg/L	1600	1632
Ca	mg/L	600	620
Mg	mg/L	388	395

3.2 Characterization of Fe_3O_4 Nanoparticles

3.2.1 XRD Analysis

Different pH values were used to investigate the influence of different pHs on the nanoparticles, and the XRD patterns. The strong peaks at $2\theta = 20.08$ of the curve were attributed to the presence of chitosan. When the pH values were 1.0 and 2.0. The characteristic XRD peaks at 2θ were 30.05, 35.60, 43.02, 57.03, 62.70 indicated that the nanoparticles were magnetite with an inverse spinel structure. The Fe_3O_4 existed in ion form when the pH was lower than 2.6. In contrast, the predominant form of Fe_3O_4 is colloidal at pH 3.0 and 3.5, which greatly affected the crystallinity of the nanoparticles obtained. The results of XRD indicated that the feasible pH for the synthesis should be below 2.0 (Baiju *et al.* 2018).

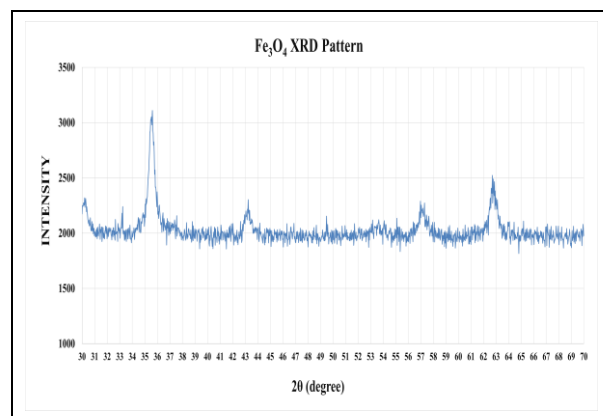


Fig. 4: X-ray diffractogram

3.2.2 FTIR Analysis

The functional groups present in the Fe_3O_4 nanoparticles monitored by FT-IR spectroscopy and the interval of 600–750 $^\circ\text{C}$, the weight-loss percentages of chitosan and pure Fe_3O_4 were approximately 3% and 0.2% without any change of heat flow. In contrast, the weight-loss percentage of sample was nearly 9% with a significant exothermic peak, which is assigned to the chemical interactions between the Fe_3O_4 nanoparticles and chitosan. It is possible that these interactions increased the decomposition temperature of the chitosan coating the Fe_3O_4 nanoparticles. Most of the chitosan thermally decomposed completely before 600 $^\circ\text{C}$, however, the chitosan coating the Fe_3O_4 nanoparticles decomposed completely only when temperature was up to 750 $^\circ\text{C}$. FT-IR analysis was performed to characterize the surface nature of Fe_3O_4 nanoparticles. The characteristic bands at 3500 cm^{-1} corresponded to the stretching vibration of $-\text{NH}_2$ group and $-\text{OH}$ group, and the bands at 2775, 2075, 1890 and 1400 cm^{-1} represented the presence of $-\text{CH}$ and $-\text{CH}_2$ group. The characteristic band at 1056 cm^{-1} represented the presence of the $-\text{C}-\text{O}-$ group of chitosan. The disappearance of the “free” aminogroup absorption band in sample is most probably due to chelation of

amino groups with the magnetite nanoparticles. Based on the result of FT-IR, the magnetite nanoparticles were coated by chitosan layer via the amino group of chitosan. (Baiju *et al.* 2018) and shown in Fig. 5.

3.2.3 SEM Morphology

SEM morphologies of the magnetite nanoparticles in chitosan. The pH values of the solution strongly affect the morphologies of Fe₃O₄ nanoparticles. When pH values were lesser than 2.0, the nanoparticles had diameters smaller than 0.15µm, an oval shape, and were uniformly dispersed in the chitosan hydrogel without aggregation. The average size of Fe₃O₄ nanoparticles from SEM was larger than the result from the Scherrer formula (11 nm), which was attributed to the fact that the Scherrer formula only provides the lower limit on mean crystallite size. The diameter of the Fe₃O₄ nanoparticles indicated that the Fe₃O₄ nanoparticles are super paramagnetic. It is confirmed that the nanoparticles

were Fe₃O₄ with an inverse spinel structure again (Baiju *et al.* 2018) and shown Fig. 6.

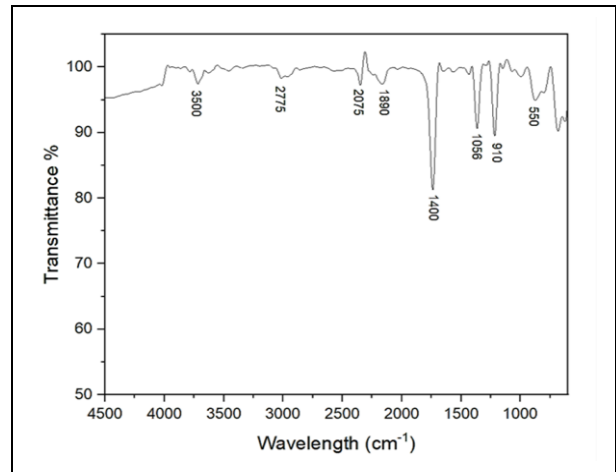


Fig. 5: FTIR Spectrum

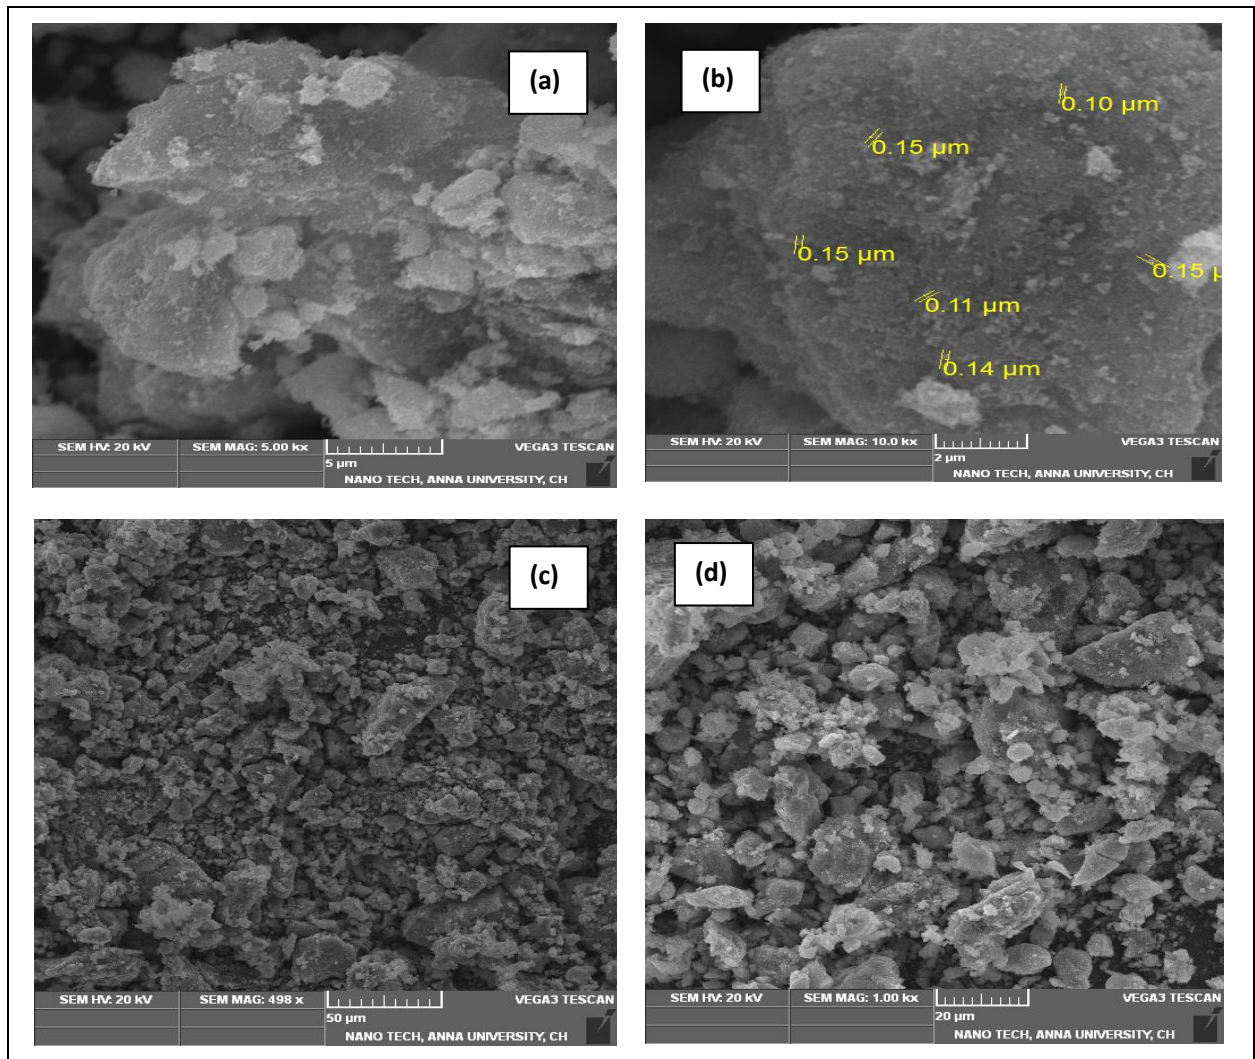


Fig. 6: SEM image of FeMoPO Nanoparticles

3.3 EF Results

3.3.1 Effect of Catalyst Dosage

In heterogeneous E-Fenton process, effect of catalyst dosage is studied by varying dosages from 25 mg/L to 100 mg/L. The other operating parameters were maintained constant (i.e) initial pH 3, voltage 5 V, electrode spacing 3cm. the COD removal increases when the catalyst dosage increases till it reaches saturation point after which the removal efficiency decreases. Excessive catalyst dosages lead to the surplus Fe^{2+} acting as a hydroxyl radical scavenger, subsequently oxidizing to Fe^{3+} . This process diminishes the availability of hydroxyl radicals for the oxidation of pollutants, resulting in reduced COD removal efficiency. Conversely, lower catalyst dosages inadequately produce Fe^{2+} , limiting the hydroxyl radical generation and consequently lowering COD removal efficiency (Oturán *et al.* 2001). The optimum catalyst dosage for electro-Fenton process is 50 mg/L at 90 minutes, the plotted graph is given in Fig. 7.

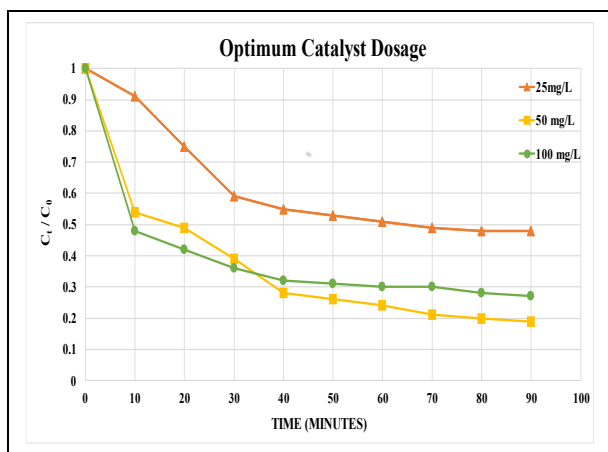


Fig. 7: Optimum catalyst dosage chart

3.3.2 Effect of pH

To investigate the effect of pH on E-Fenton process, studies were performed by varying pH from 1.5 to 5. The other parameters that was constant were catalyst dosage 50 mg/L, voltage 5 V and electrode spacing of 3 cm. The optimum pH for heterogeneous E-Fenton process was found to be 2 with a removal efficiency of 84% and the plotted graph is given in Fig. 8. As the pH was increased from 2 to 5, removal efficiency decreased from 84% to 53%. This may be due to the iron complexes formed at high pH (Nidheesh *et al.* 2014). Also the advantage of employing the Fenton process at a low pH, specifically between 2 and 3, lies in its effectiveness for eliminating inorganic carbons from wastewater. At this acidic pH range, the Fenton process exhibits a high removal efficiency, with the optimal outcome observed at pH 2. This underscores the significance of maintaining a low pH to enhance the performance of the electro-

Fenton process in wastewater treatment (Zhang *et al.* 2005).

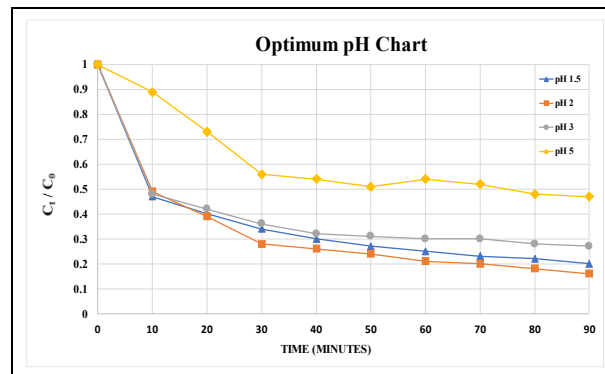


Fig. 8: Optimum pH dosage chart

3.3.3 Effect of Electrode Spacing

The effect of electrode spacing in heterogeneous E-Fenton process is done by varying the electrode spacing from 2 cm to 4 cm. The other operating parameters that were kept constant are catalyst dosage 50 mg/L, pH 2 and voltage 5 V. When the electrode spacing is increased to 4 cm, it results in a longer path for the electric current to travel, leading to increased ohmic drop. This higher resistance hinders the electrochemical reactions, particularly affecting the mass transfer of Fe^{3+} , which is essential for in removing COD. When the electrode spacing is reduced to 2 cm, the efficiency further dropped due to the faster electro-generation of Fe^{2+} to Fe^{3+} at the anode. The optimum electrode spacing for heterogeneous E-Fenton process is found to be 3 cm.

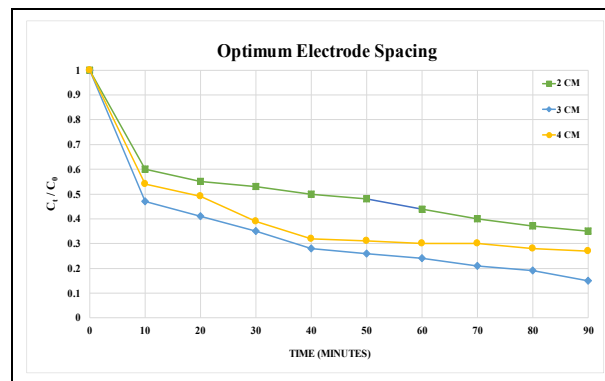


Fig. 9: Optimum electrode spacing chart

Leachate characterization after E-Fenton treatment was done as per standard methods and the obtained results are given in Table 2. The characterisation was done for the effluent which was treated at optimum conditions (i.e.) catalyst dosage of 50 mg/L, pH of 2 and electrode spacing of 3 cm. The effluent had an average pH of 1.985 and BOD/COD value of 0.5155, and can observe good amount of improvement in the quality of leachate, as the BOD/COD value increased from 0.169 to 0.515. COD of E-Fenton treated leachate

is 1090.5 mg/L which has removal efficiency of 84.29%. It is observed that TSS, Cl, Ca, Mg values were also reduced after the E-Fenton treatment. EC, TDS values increased after the treatment. There is a significant improvement in colour of the treated leachate.

Table 2. Characteristics of E-Fenton treated landfill leachate

Experiment	Unit	Effluent		Average
pH	-	1.98	1.99	1.985
EC	μS/cm	41097	41918	41507.5
BOD5	mg/L	557	568	562.5
COD	mg/L	1069	1112	1090.5
BOD5/COD	-	0.521	0.510	0.5155
TDS	mg/L	49315	50301	49808
TSS	mg/L	435	440	437.5
TS	mg/L	49750	50741	50245.5
Cl	mg/L	1584	1617	1600.5
Ca	mg/L	589	602	595.5
Mg	mg/L	382	399	390.5

3.4 CW Results

The treated effluent obtained from the Electro Fenton process underwent mixing with activated sludge and wastewater from the Anna University Sewage Treatment Plant, Chennai in 1:1:1 ratio. This resultant mixture was employed as the influent for the experimental setup which helps in inoculating the wetland setup and increases the microbial activity. The experiments were conducted in a batch process, with two trials performed to assess the consistency of the treatment process. To maintain a balance between treatment efficiency and evaporation loss, the Hydraulic Retention Time (HRT) was carefully chosen as 3 days with working volume as 3 Litres. The eggshells has high adsorptive capacity to inorganic compounds, which can be attributed to their expansive surface area, featuring numerous pores ranging between 7,000 and 17,000. This inherent high porosity and natural composition helps in the utilization of eggshells in their natural state without the need for surface activation process (Zonato *et al.* 2022). Leachate characterization after Constructed Wetland treatment was done as per standard methods and the obtained results are given in Table 3. The effluent had an average pH of 7.315 and BOD/COD value of 0.645, and good amount of improvement in the quality of leachate was observed, as the BOD/COD value increased from 0.169 to 0.645. COD of CW treated leachate is 292 mg/L which has removal efficiency of 95.79%. It is observed that TSS, Cl, Ca, Mg values were also reduced after the CW treatment. EC, TDS values increased after the treatment. While comparing CW1 and CW2, all parameters were improved except Ca and Mg concentrations. This may be due to the presence of eggshell in the intermediate layer of CW2. Eggshells, rich in calcium carbonate, serve as excellent adsorbent materials for the remediation of contaminated water. Consequently, the utilization of eggshells in treatment processes leads to an elevation in

the concentration of calcium in the effluent (Lee *et al.* 2022). There is a significant improvement in colour of the treated leachate in both systems. Comparing the CW-2 with control system CW-1 it was found that CW-2 gave better results than CW-1 except for few parameters, hence using eggshell as a wetland substrate not only an economical but also an efficient alternative in treating leachate.

Table 3. Characteristics of Constructed Wetland treated landfill leachate

Experiment	Unit	Effluent					
		Sand+ Gravel+		Average	Sand+ Eggshell+		Average
		Gravel	Gravel		Gravel	Gravel	
pH	-	7.15	6.9	7.025	7.4	7.23	7.315
EC	μS/cm	22648	23100	22874	20426	20822	20624
BOD5	mg/L	209	213	211	187	190	188.5
COD	mg/L	331	337	334	293	291	292
BOD5/COD	-	0.631	0.632	0.6315	0.638	0.652	0.645
TDS	mg/L	22191	22600	22395	19357	19744	19550
TSS	mg/L	174	182	178	153	158	155.5
TS	mg/L	22365	22782	22573.5	19510	19902	19706
Cl	mg/L	633	649	641	596	611	603.5
Ca	mg/L	177	181	179	209	215	212
Mg	mg/L	116	123	119.5	143	147	145

4. CONCLUSION

In the present study, heterogeneous E-Fenton process was used in treating for stabilized landfill leachate using Fe₃O₄ nanoparticles. The Fe₃O₄ nanoparticles was obtained by synthesizing chitosan via iron ions assembly and this was used as a catalyst. The results indicated that COD was reduced from 6945 mg/L to 1090.5 mg/L with removal efficiency of 84.29%. COD removal was achieved at optimal conditions of pH 2, catalyst dosage 50 mg/L and electrode spacing of 3cm. After the Electro Fenton process, an enhancement in the biodegradability was observed from the BOD5/COD ratio when it increased from 0.03 to 0.51. Subsequent biological treatment using Constructed Wetland using eggshell as the substrate further reduced the COD to 292 mg/L and the BOD5/COD ratio increased from 0.51 to 0.645. This also proved that using eggshells as a media is a reliable alternative compared to regular sand media but the Ca and Mg concentrations in final effluent treated by CW-2 was more compared to control system CW-1. Combined E- Fenton and biological treatment (CW) achieved an overall COD removal of 95.79% and increased the biodegradability effectively proving this integration to be a proficient treatment for stabilized landfill leachate.

FUNDING

This research received no specific grant from any funding agency in the public, commercial, or not-for-profit sectors.

CONFLICTS OF INTEREST

The authors declare that there is no conflict of interest.

COPYRIGHT

This article is an open-access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<http://creativecommons.org/licenses/by/4.0/>).



REFERENCES

- Aragaw, T. A., Bogale, F. M., Aragaw, B. A., Iron-based nanoparticles in wastewater treatment: A review on synthesis methods, applications, and removal mechanisms, *J. Saudi Chem. Soc.* 25(8), 101280 (2021).
<https://doi.org/10.1016/j.jscs.2021.101280>
- Baiju, A., Gandhimathi, R., Ramesh, S. T., Nidheesh, P. V., Combined heterogeneous Electro-Fenton and biological process for the treatment of stabilized landfill leachate, *J. Environ. Manage.* 210, 328–337 (2018).
<https://doi.org/10.1016/j.jenvman.2018.01.019>
- Bakhshoodeh, R., Alavi, N., Oldham, C., Santos, R. M., Babaei, A. A., Vymazal, J., Paydary, P., Constructed wetlands for landfill leachate treatment: A review, *Ecol. Eng.* 146, 105725 (2020).
<https://doi.org/10.1016/j.ecoleng.2020.105725>
- Bandala, E. R., Liu, A., Wijesiri, B., Zeidman, A. B., Goonetilleke, A., Emerging materials and technologies for landfill leachate treatment: A critical review, *Environ. Pollut.* 291, 118133 (2021).
<https://doi.org/10.1016/j.envpol.2021.118133>
- Bhatt, P., Joshi, S., Urper Bayram, G. M., Khati, P., Simsek, H., Developments and application of chitosan-based adsorbents for wastewater treatments, *Environ. Res.* 226, 115530 (2023).
<https://doi.org/10.1016/j.envres.2023.115530>
- Chelu, M., Musuc, A. M., Popa, M., Calderon Moreno, J. M., Chitosan Hydrogels for Water Purification Applications, *Gels* 9(8), 664 (2023).
<https://doi.org/10.3390/gels9080664>
- Deng, Y., Physical and oxidative removal of organics during Fenton treatment of mature municipal landfill leachate, *J. Hazard. Mater.* 146(1–2), 334–340 (2007).
<https://doi.org/10.1016/j.jhazmat.2006.12.026>
- Klidi, N., Proietto, F., Vicari, F., Galia, A., Ammar, S., Gadri, A., Scialdone, O., Electrochemical treatment of paper mill wastewater by electro-Fenton process, *J. Electroanal. Chem.* 841, 166–171 (2019).
<https://doi.org/10.1016/j.jelechem.2019.04.022>
- Kosmulski, M., The pH dependent surface charging and points of zero charge. IX. Update, *Adv. Colloid Interface Sci.* 296, 102519 (2021).
<https://doi.org/10.1016/j.cis.2021.102519>
- Lee, J.-I., Kim, J.-M., Yoo, S.-C., Jho, E. H., Lee, C.-G., Park, S.-J., Restoring phosphorus from water to soil: Using calcined eggshells for P adsorption and subsequent application of the adsorbent as a P fertilizer, *Chemosphere* 287, 132267 (2022).
<https://doi.org/10.1016/j.chemosphere.2021.132267>
- Nidheesh, P. V., Gandhimathi, R., Velmathi, S., Sanjini, N. S., Magnetite as a heterogeneous electro Fenton catalyst for the removal of Rhodamine B from aqueous solution, *RSC Adv.* 4(11), 5698 (2014).
<https://doi.org/10.1039/c3ra46969g>
- Oturan, M. A., Oturan, N., Lahitte, C., Trevin, S., Production of hydroxyl radicals by electrochemically assisted Fenton's reagent, *J. Electroanal. Chem.* 507(1–2), 96–102 (2001).
[https://doi.org/10.1016/S0022-0728\(01\)00369-2](https://doi.org/10.1016/S0022-0728(01)00369-2)
- Sohail, A. and Afzal, H. K., Landfill practice in India: A review, *J. Chem. Pharm. Res.*, 3(4), 270-279 (2011).
- Wang, Y., Li, B., Zhou, Y., Jia, D., Chitosan-induced synthesis of magnetite nanoparticles via iron ions assembly, *Polym. Adv. Technol.* 19(9), 1256–1261 (2008).
<https://doi.org/10.1002/pat.1121>
- Wdowczyk, A., Szymańska-Pulikowska, A., Gałka, B., Removal of selected pollutants from landfill leachate in constructed wetlands with different filling, *Bioresour. Technol.* 353, 127136 (2022).
<https://doi.org/10.1016/j.biortech.2022.127136>
- Yaashikaa, P. R., Kumar, P. S., Nhung, T. C., Hemavathy, R. V., Jawahar, M. J., Neshanthini, J. P., Rangasamy, G., A review on landfill system for municipal solid wastes: Insight into leachate, gas emissions, environmental and economic analysis, *Chemosphere* 309, 136627 (2022).
<https://doi.org/10.1016/j.chemosphere.2022.136627>
- Zhang, H., Choi, H. J., Huang, C.-P., Optimization of Fenton process for the treatment of landfill leachate, *J. Hazard. Mater.* 125(1–3), 166–174 (2005).
<https://doi.org/10.1016/j.jhazmat.2005.05.025>
- Zonato, R. de O., Estevam, B. R., Perez, I. D., Aparecida dos Santos Ribeiro, V., Boina, R. F., Eggshell as an adsorbent for removing dyes and metallic ions in aqueous solutions, *Clean. Chem. Eng.* 2, 100023 (2022).
<https://doi.org/10.1016/j.clce.2022.100023>
- Zijing, G., Yang, Z., Hui, J., Jiaran, G., Xia, M., Jie, W., Electrochemical methods for landfill leachate treatment: A review on electrocoagulation and electrooxidation, *Sci. Total Environ.*, 806, 150529 (2022).
<https://doi.org/10.1016/j.scitotenv.2021.150529>